arXiv:cond-mat/0604612v4 [cond-mat.str-el] 1 Feb 2007

Universal Scaling in the Dynamical Conductivity of Heavy Fermion Ce and Yb Compounds

Hidekazu Okamura*, Tatsuya Watanabe[1], Masaharu Matsunami[1], Tomohisa Nishihara[1], Naohito Tsujii[2], Takao Ebihara[3], Hitoshi Sugawara[4], Hideyuki Sato[5], Yoshichika Ōnuki[6], Yosikazu Isikawa[7], Toshiro Takabatake[8] and Takao Nanba[1]

[1] *Graduate School of Science and Technology, Kobe University, Kobe 657-8501*
[2] *National Institute for Materials Science, Tsukuba 305-0047*
[3] *Department of Physics, Faculty of Science, Shizuoka University, Shizuoka 422-8529*
[4] *Faculty of Integrated Arts and Sciences, University of Tokushima, Tokushima 770-8502*
[5] *Graduate School of Science, Tokyo Metropolitan University, Tokyo 192-0397*
[6] *Graduate School of Science, Osaka University, Toyonaka 560-0043*
[7] *Department of Physics, Toyama University, Toyama 930-8555*
[8] *Graduate School of Quantum Matter, Hiroshima University, Higashi-Hiroshima 739-8526*

(Received February 6, 2008)

Dynamical conductivity spectra [$\sigma(\omega)$] have been measured for many heavy-fermion (HF) Ce and Yb compounds. A characteristic excitation peak has been observed in the infrared region of $\sigma(\omega)$ for all the compounds, and has been analyzed in terms of a simple model based on conduction (c)-f electron hybridized band. A universal scaling is found between the observed peak energies and the estimated c-f hybridization strengths of these HF compounds. This scaling demonstrates that the model of c-f hybridized band can generally and quantitatively describe the low-energy charge excitations in a wide range of HF compounds.

KEYWORDS: Heavy fermion, optical conductivity

Physics of "heavy fermion (HF)" compounds has attracted a considerable amount of interest during the last few decades. In HF compounds, a strong Coulomb correlation of the f electrons enhances the carrier effective mass (m^*). The mass enhancement is manifested in, e.g., the quadratic temperature (T) coefficient (A) of the resistivity and the linear T coefficient (γ) of the electronic specific heat.[1] It has been shown that a scaling between A and γ^2, now widely known as the "Kadowaki-Woods (KW) relation", holds for a large number of HF compounds having different degrees of mass enhancement and orbital degeneracy.[2,3] Theoretically, the KW relation including effects of electron correlation was successfully derived using the periodic Anderson model (PAM),[4] and later generalized to include effects of orbital degeneracy.[3,5] In addition to the interesting transport, magnetic, and thermal properties of HF compounds, their charge excitation spectra, measured as the dynamical (optical) conductivity $\sigma(\omega)$, have been shown to be highly anomalous compared with those of conventional metals.[6,7] Such anomalies should arise from their peculiar electronic dispersion near the Fermi level (ϵ_F), which is the main interest of this Letter.

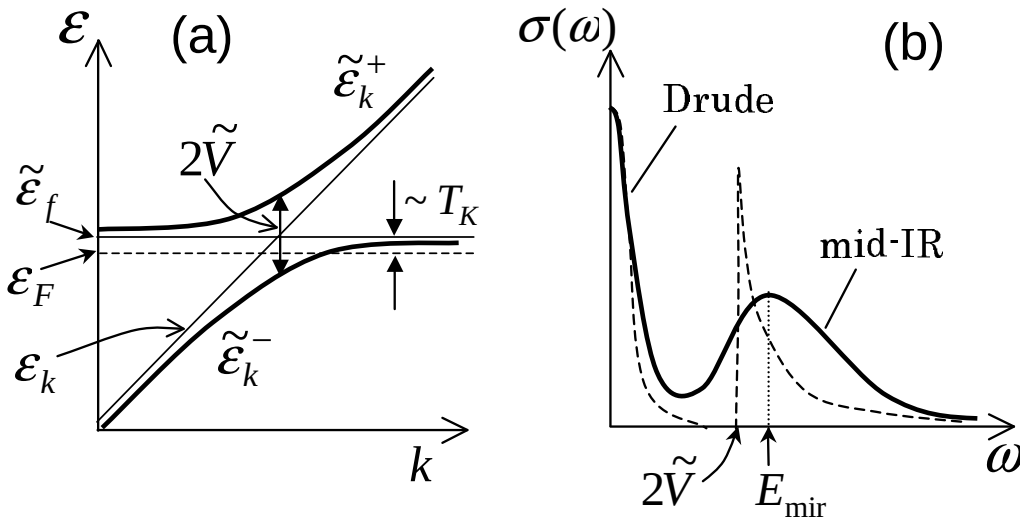

Fig. 1. (a) Dispersion of the renormalized hybridized bands near ϵ_F, expressed as $\tilde{\epsilon}_k^{\pm} = \frac{1}{2}[\tilde{\epsilon_f} + \epsilon_k \pm \sqrt{(\tilde{\epsilon_f} - \epsilon_k)^2 + 4\tilde{V}^2}]$.[8–10] Here $\tilde{\epsilon_f}$ and $\tilde{V}$ are renormalized f level and c-f hybridization, respectively. ϵ_k is the bare c band dispersion and $T_{\rm K}$ is the Kondo temperature. (b) Sketch of $\sigma(\omega)$ expected from $\tilde{\epsilon}_k^{\pm}$.[11,12] The dashed and solid curves show those without and with disorder-induced broadening, respectively.

The simplest case of a HF compound is that of a Ce (Yb) compound with a $4f^1$ ($4f^{13}$) configuration, where a $4f$ electron (hole) interacts with the conduction electrons.[1] Using the Fermi liquid theory and PAM, it has been shown that the dispersion in such a case may be approximated in terms of "renormalized hybridized bands", as sketched in Fig. 1(a).[8–10] They result from a conduction (c)-f electron hybridization renormalized by the electron correlation. The $\sigma(\omega)$ spectrum resulting from this dispersion consists of a very narrow Drude peak centered at ω=0[11] and a peak at finite energy due to interband transitions [Fig. 1(b)].[12] Experimentally, $\sigma(\omega)$ of several HF compounds exhibited a narrow Drude peak[7] and a mid-infrared (mid-IR) absorption peak,[13–16] which were consistent with the predictions in Fig. 1(b). Garner *et al*[13] first pointed out that, according to results of c-f hybridized bands,[10] the position (energy) of the mid-IR peak in $\sigma(\omega)$, $E_{\rm mir}$, should obey

$$E_{\rm mir} \propto \sqrt{T_K W}, \qquad (1)$$

where W is the bare c band width. Degiorgi *et al.*[14] also discussed $E_{\rm mir}$ of HF compounds using Eq. (1), while Dordevic *et al.*[15] reported a scaling of $E_{\rm mir}$ for a few HF compounds, using a relation essentially equivalent to Eq. (1). Subsequently, Hancock *et al.*[16] used Eq. (1) to analyze $\sigma(\omega)$ spectra of $\mathrm{YbIn}_{1-x}\mathrm{Ag}_x\mathrm{Cu}_4$. They showed that E_{mir} indeed scaled with $\sqrt{T_K}$ for $0 \leq x \leq 1$, establishing a scaling of E_{mir} in terms of Kondo physics for $\mathrm{YbIn}_{1-x}\mathrm{Ag}_x\mathrm{Cu}_4$. However, since these previous works dealt with a limited range of HF compounds, it was unclear whether such a scaling of mid-IR peak based on c-f hybridized band was universal for many HF compounds.

---

*E-mail: okamura@kobe-u.ac.jp

In this Letter, $\sigma(\omega)$ spectra of many Ce- and Yb-based HF compounds are systematically examined to test whether the mid-IR peaks follow a universal law among these compounds, and to clarify the above question. $\sigma(\omega)$ of CeNi, CeSn_3, YbInCu_4, YbAl_2, $\mathrm{YbCu}_2\mathrm{Si}_2$, $\mathrm{YbNi}_2\mathrm{Ge}_2$, and YbCuAl have been newly measured. $\sigma(\omega)$ spectra are also taken from our previous works on CeNiSn,[17] CeRhSb,[17] $\mathrm{CeOs}_4\mathrm{Sb}_{12}$,[18] $\mathrm{CeRu}_4\mathrm{Sb}_{12}$[19] and YbAl_3.[21] In addition, several other HF compounds for which E_{mir} values have been reported in the literature are considered. Table I lists the physical parameters of the studied HF compounds, used below to evaluate their T_{K} and W. Note that these compounds span a wider range of γ values compared with previous works,[7,15,16] which is important for our purpose. It is shown that their E_{mir} values scale well in the form of Eq. (1).

The newly measured samples were polycrystals for YbAl_2 and YbCuAl,[22] and single crystals for CeNi,[38] CeSn_3,[33] YbInCu_4,[44] $\mathrm{YbNi}_2\mathrm{Ge}_2$[22] and $\mathrm{YbCu}_2\mathrm{Si}_2$.[45] The optical reflectivity spectra $[R(\omega)]$ were measured on as-grown specular surfaces for $\mathrm{YbCu}_2\mathrm{Si}_2$ and $\mathrm{YbNi}_2\mathrm{Ge}_2$, on cleaved surfaces for CeNi and YbInCu_4,[20] and on polished surfaces for the others. $\sigma(\omega)$ spectra were obtained from $R(\omega)$ using the Kramers-Kronig analysis. Other details were similar to those described elsewhere.[21]

Figure 2 shows the obtained $\sigma(\omega)$ spectra at 9 K. Since the dispersion sketched in Fig. 1 does not include thermal effects, here we discuss low-T spectra only. All these compounds clearly exhibit a mid-IR peak in $\sigma(\omega)$, which strongly suggests that the appearance of a mid-IR peak is a universal property of the HF compounds. Their E_{mir}'s (peak positions), indicated by the arrows in Fig. 2, vary markedly from compound to compound, which indicates a wide range of their $\tilde{V}$ and T_K. Our $\sigma(\omega)$ spectra of CeSn_3 and $\mathrm{CeRu}_4\mathrm{Sb}_{12}$ are similar to those in Refs.,[15,46] although the overall magnitude of our $\sigma(\omega)$ is larger. Our E_{mir} of 0.25 eV for YbInCu_4, measured on a cleaved sample, agrees with the previously reported value[16] for a polished sample, while the overall magnitude of our $\sigma(\omega)$ is much smaller.[20]

Eq. (1) can be derived from the relation $2\tilde{V} \propto \sqrt{T_{\mathrm{K}} W}$,[10] which is a result of PAM, and by setting $E_{\mathrm{mir}} \propto 2\tilde{V}$. Although E_{mir} is larger than $2\tilde{V}$ as sketched in Fig. 1(b), Hancock *et al.*[16] have well demonstrated that $E_{\mathrm{mir}} \propto 2\tilde{V}$ holds in fact for $\mathrm{YbIn}_{1-x}\mathrm{Ag}_x\mathrm{Cu}_4$ ($0 \leq x \leq 1$). To analyze the measured E_{mir} values using Eq. (1), it should be expressed in terms of experimentally observable quantities. W of a Ce (Yb) compound may be regarded as inversely proportional to γ of the non-magnetic, isostructural La (Lu) compound (denoted as γ_0). Concerning T_{K}, since we need to deal with a large number of compounds, we shall make use of the simple relation[1]

$$T_{\mathrm{K}} = \pi^2 N_{\mathrm{A}} k_{\mathrm{B}} a/(3\gamma). \tag{2}$$

Here, N_{A} and k_{B} are the Avogadro number and Boltzman constant, respectively, and a is a constant which depends only on the f level degeneracy N: a=0.21, 0.54 and 0.59 for N=2, 6 and 8, respectively.[1] Then Eq. (1) can be rewritten as

$$E_{\mathrm{mir}} \propto \sqrt{a/(\gamma\gamma_0)}. \tag{3}$$

The constant of proportionality in Eq. (3) is, in the absence of broadening ($E_{\mathrm{mir}} = 2\tilde{V}$), given as

$$S_{\mathrm{th}} = \sqrt{8\pi^3/9} \cdot N_{\mathrm{A}} k_{\mathrm{B}}^2, \tag{4}$$

which is material independent.

In analyzing the experimental E_{mir} values using Eqs. (3) and (4), we also include reported E_{mir}'s in the literature for YbAgCu_4,[16] $\mathrm{YbRh}_2\mathrm{Si}_2$,[47] CePd_3[46] and CeCu_6.[42] Except for $\mathrm{CeRu}_4\mathrm{Sb}_{12}$[39] and $\mathrm{YbRh}_2\mathrm{Si}_2$,[31] the HF compounds have Fermi liquid (FL) ground state at low T. Their γ values in Table I are taken from the cited

Table I. Specific heat coefficients (γ) of the Yb (Ce) compounds and those (γ_0) of the isostructural Lu (La) compounds in units of mJ/K^{2}mol. The γ values marked with asterisks are not from the cited references, but from our own analysis to separate a NFL contribution from the total γ reported in the cited references.[31,39]

	γ	γ_0		γ	γ_0
YbAl_2	17^{22}	5.6^{23}	CeSn_3	53^{33}	2.5^{34}
YbAl_3	58^{24}	4^{25}	CePd_3	38.6^{35}	3.5^{36}
$\mathrm{YbCu}_2\mathrm{Si}_2$	135^{22}	3^{26}	CeRhSb	$23\text{-}28^{37}$	8.2^{37}
$\mathrm{YbNi}_2\mathrm{Ge}_2$	136^{22}	12.7^{27}	CeNi	57^{38}	5^{38}
YbCuAl	260^{22}	5.9^{28}	CeNiSn	51^{37}	11.4^{37}
YbInCu_4	50^{29}	8.7^{30}	$\mathrm{CeRu}_4\mathrm{Sb}_{12}$	$50\text{-}85^{*39}$	37^{39}
YbAgCu_4	210^{29}	10^{29}	$\mathrm{CeOs}_4\mathrm{Sb}_{12}$	92^{40} 180^{41}	36^{40}
$\mathrm{YbRh}_2\mathrm{Si}_2$	$100\text{-}140^{*31}$	7.8^{32}	CeCu_6	1600^{42}	8^{42}

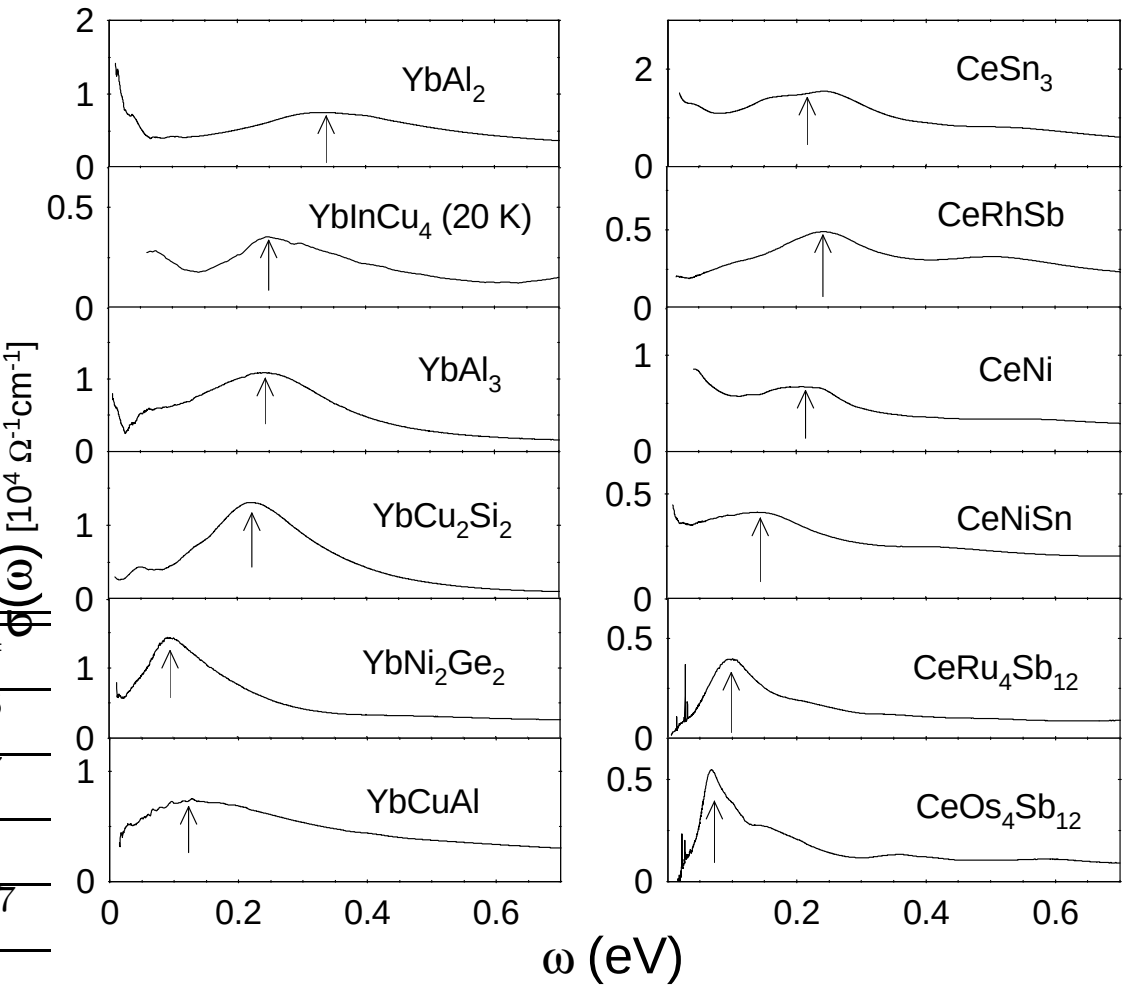

Fig. 2. Measured $\sigma(\omega)$ at 9 K, except for YbInCu_4 measured at 20 K for technical limitation. The arrows indicate the E_{mir} values (peak positions) of the mid-IR peaks.

references, which were determined through the usual procedure, i.e., by extrapolating the measured C_e/T to T=0 (C_e is the electronic specific heat). The γ value thus obtained is the "Kondo contribution" proportional to $1/T_K$ as discussed above. CeRu$_4$Sb$_{12}$[39] and YbRh$_2$Si$_2$[31] show steep rise in C_e/T due to non-Fermi liquid (NFL) properties below $\sim$ 4 K and $\sim$ 10 K, respectively. Such a NFL effect is not included in our simple model of Eq. (2). However, since the onset T of this "NFL contribution" is clearly identified in their T dependence of C_e/T,[31,39] it can be subtracted from the total C_e/T to estimate a Kondo contribution,[31,39] as previously done for, e.g., another NFL compound CeRhSn.[50] (Of course, there is no rigorous theoretical justification for this subtraction, since the NFL properties should also arise from the strong electron correlation. However, it is a simple, phenomenological scheme to estimate the underlying Kondo coupling of an NFL compound.[50]) Their γ's in Table I are the Kondo contributions thus obtained.[31,39] Estimated uncertainty resulting from the subtraction is indicated by the horizontal error bars in Fig. 3, which are rather small since not γ but $\sqrt{\gamma}$ enters Fig. 3. CeOs$_4$Sb$_{12}$ shows a gradual increase of resistivity below 50 K, although other physical properties show metallic characteristics including the C_e/T data.[40,41] CeNiSn and CeRhSb are metals having low carrier densities (n) and a reduced density of states (dos) at ϵ_F.[37] The reported E_mir's of YbFe$_4$Sb$_{12}$[15,48] and CeCoIn$_5$[49] are not included here, since YbFe$_4$Sb$_{12}$ is not an f electron-derived HF,[48] and since CeCoIn$_5$ shows strong NFL properties up to high T,[51] making it difficult to estimate the Kondo contribution to γ.

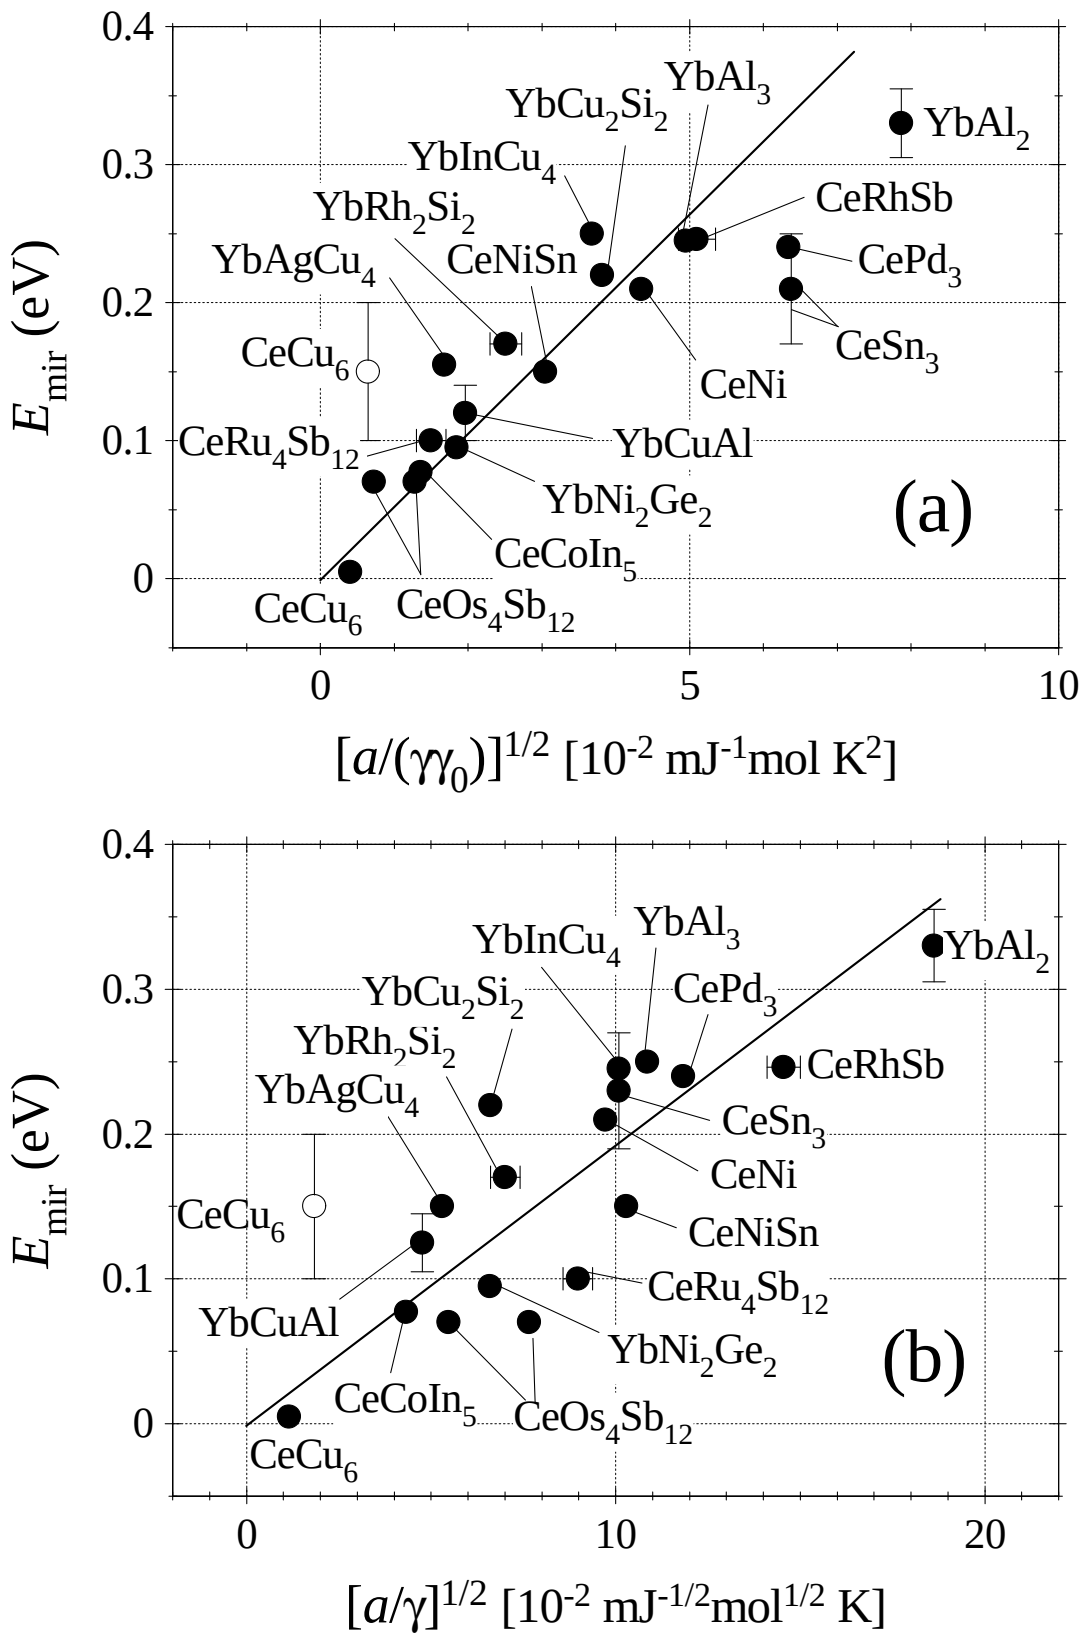

Fig. 3. Mid-IR peak energies (E_mir) plotted as a function of (a) $\sqrt{a/(\gamma\gamma_0)}$ and (b) $\sqrt{a/\gamma}$. The solid lines are guide to the eye. The horizontal error bars indicate the uncertainties in γ and the vertical ones those in determining E_mir due to broad lineshapes.

Figure 3(a) shows plots of the measured and reported E_mir values as a function of $\sqrt{a/(\gamma\gamma_0)}$ using the γ and γ_0 values in Table I. Here, N=8 (6) has been used for the Yb (Ce) compounds, except for CeCu$_6$ (see below). Figure 3(a) shows that the E_mir values scale well, in agreement with the prediction of Eq. (3). Some of the compounds, e.g., YbAl$_2$, CePd$_3$, CeSn$_3$ and CeCu$_6$, seem to show larger deviations than the others. However, considering the extreme simplicity of our model, the overall scaling is still good. The reported $\sigma(\omega)$ of CeCu$_6$ at low T shows two marked IR peaks: a broad one centered at $\sim$ 0.15 eV and the other at 5 meV.[42] Since the energy scale of 0.15 eV (1700 K) is much larger than T_K of CeCu$_6$ ($\sim$ 1 K),[42] the 5 meV peak rather than the 0.15 eV peak should be associated with the hybridization gap, as previously done.[15] Hence only the 5 meV peak is plotted in Fig. 3(a) using N=2 since the Ce ground state in CeCu$_6$ is a N=2 doublet due to crystal field splitting. (See the discussion below regarding the lowering of degeneracy in other compounds.) From Fig. 3(a), the experimental slope of the scaling is estimated as S_ex = (7 $\sim$ 9) $\times$ 10^{-22} J^2/K^{2}mol, which is in excellent agreement with the theoretical slope given by Eq. (4), S_th=6.0 $\times$ 10^{-22} J^2/K^{2}mol. (Note that the actual $2\tilde{V}$ is slightly smaller than E_mir, as mentioned before.) For comparison, in Fig. 3(b) E_mir is plotted as a function of $\sqrt{a/\gamma}$ ($\propto \sqrt{T_\mathrm{K}}$), without including γ_0 ($\propto W^{-1}$). Although an overall tendency for scaling is still seen, it is much less satisfactory than that in Fig. 3(a). This is in contrast to the previous result of good scaling without W observed for YbIn$_{1-x}$Ag$_x$Cu$_4$.[16] Clearly, the explicit inclusion of W ($\propto \gamma_0^{-1}$) in our analysis has been crucial for observing the good scaling over many HF compounds. Note that CeNiSn and CeRhSb show good scaling of E_mir despite their small n,[37] while they are completely off the KW relation.[3] These contrasting results are reasonable, since S_th does not depend on n, while the slope of KW relation does depend on n.[3] Figure 3(a) convincingly demonstrates that the universal relation predicted by Eqs. (2) and (3) is in fact followed by these HF compounds, and that the model of c-f hybridized band has captured the essential physics involved in the low-energy dynamical conductivity of HF compounds.

The Ce or Yb ground state is a doublet also in CeNiSn,[37] YbCu$_2$Si$_2$[3] and YbRh$_2$Si$_2$.[31] Hence the T_K estimated from their γ at low T correspond to that of the N=2 ground state. However, except for the 5 meV peak for CeCu$_6$,[42] their mid-IR peaks have a large energy scale of the order of 1000 K. Hence the mid-IR peaks should be associated with the "high-temperature T_K" (T_K^h) for the entire J=5/2 (7/2) multiplet with N=6 (8). Since T_K^h is larger than the ground state T_K, our use of γ at low T should underestimate T_K^h relevant to the mid-IR peak. In spite of this, these compounds are scaled well in Fig. 3(a). This is probably because our use of N=6 (8) has partly compensated for the underestimation of T_K^h: in the relation $T_\mathrm{K} \propto a/\gamma$, a=0.54 (0.59) for N=6 (8) is greater than

a=0.21 for N=2.[1] It is also remarkable that the two NFL compounds, $YbRh_2Si_2$ and $CeRu_4Sb_{12}$, scale reasonably well, once the Kondo contribution is separated from the total C_e/T.

Regarding the c-f hybridized band model in Fig. 1, it should be recalled that only one linear combination of $4f$ orbitals can hybridize with one conduction band per spin.[8,9] When the $4f$ ground state is orbitally degenerate, as in many of the compounds studied here, the rest of the degenerate $4f$ orbitals should remain unhybridized and dispersionless at $\tilde{\epsilon}_f$.[52] They should cause a sharp f-dos at $\tilde{\epsilon}_f$, which gives rise to, e.g., a large Van Vleck susceptibility in HF compounds.[52] With such an f-dos remaining at $\tilde{\epsilon}_f$, one might expect a more complicated dispersion than that in Fig. 1, and hence a more complicated $\sigma(\omega)$ spectrum. (A detailed discussion concerning effects of f level degeneracy on the c-f hybridized state has been given.[53]) However, note that such an unhybridized f level, which is completely uncoupled from the c electron, cannot contribute to $\sigma(\omega)$.[54] This is most likely the reason why the basic features of the mid-IR peak in $\sigma(\omega)$ can be understood without taking the $4f$ orbital degeneracy into account.

The limitation of the present scaling is clear: it cannot deal with the U-based HF compounds having a f^2 or f^3 configuration. Although there have been many reports of $\sigma(\omega)$ on U compounds,[7] the hybridized band model of Fig. 1 based on f^1 configuration is not directly applicable to the U compounds. To quantitatively understand $\sigma(\omega)$ of U compounds, further progress is required in the theoretical understanding of their electronic dispersion.

In summary, it has been shown that the peak energy of the characteristic IR excitation in $\sigma(\omega)$ universally scales with the c-f hybridization strength, estimated by $\sqrt{a/(\gamma\gamma_0)}$, for many Ce- and Yb-based HF compounds. This optical scaling demonstrates that the simple model of c-f hybridization band can quantitatively account for the low-energy charge dynamics in these HF compounds. Of course, there are exceptions to the present scaling. For example, $CeAl_3$ does not exhibit an IR peak,[7] although its γ value is comparable to that of CeCu6. Such an exception is not surprising; even the KW relation, now widely regarded as being universal, breaks down for certain HF compounds.[3] The important point is that most of the Ce- and Yb-based HF compounds whose $\sigma(\omega)$ data are currently available have been considered here, and that they have shown the good scaling. In this sense, we believe that the present optical scaling for the Ce and Yb compounds should be a universal property.

H. O. would like to thank Professors T. Mutou, H. Kontani, H. Harima, and T. Saso for useful discussions. Experiments were partly performed at UVSOR BL7B as a Joint Studies Program of IMS, and at SPring-8 BL43IR under the approval by JASRI (2004A0778-NSa-np). This work has been partly supported by COE Research (No. 13CE2002), and Priority Areas "Skutterudites" (Nos. 15072204, 15072206, 15072207) and "High Field Spin Science in 100 T" (No. 451) from the Ministry of Culture, Education, Sports, Science and Technology.

1) A.C. Hewson, *The Kondo problem to heavy fermions* (Cambridge University Press, Cambridge 1993).
2) K. Kadowaki and S. B. Woods, Solid State Commun. **58**, 507 (1986).
3) N. Tsujii, H. Kontani, and K. Yoshimura, Phys. Rev. Lett. **94**, 057201 (2005); Physica B **378-380**, 730 (2006).
4) K. Yamada and K. Yosida, Prog. Theor. Phys. **76**, 621 (1986).
5) H. Kontani, J. Phys. Soc. Jpn. **73**, 515 (2004).
6) B. C. Webb, A. J. Sievers and T. Mihalisin: Phys. Rev. Lett. **57** (1986) 1951.
7) L. Degiorgi, Rev. Mod. Phys. **71** (1999) 687, and references therein.
8) T. M. Rice and K. Ueda, Phys. Rev. Lett. **55**, 995 (1985).
9) Z. Zou and P. W. Anderson, Phys. Rev. Lett. **57**, 2073 (1986).
10) D. L. Cox, Phys. Rev. Lett. **58**, 2730 (1987).
11) A. J. Millis and P. A. Lee, Phys. Rev. B **35**, 3394 (1987).
12) P. Coleman, Phys. Rev. Lett. **59**, 1026 (1987).
13) S. R. Garner, J. N. Nancock, Y. W. Rodriguez, Z. Schlesinger, B. Bucher, Z. Fisk and J. L. Sarrao: Phys. Rev. B **62** (2000) R4778.
14) L. Degiorgi, F. Anders and G. Gruner, Eur. Phys. J. B **19**, 167 (2001).
15) S. V. Dordevic, D. N. Basov, N. R. Dilley, E. D. Bauer and M. B. Maple: Phys. Rev. Lett. **86**, 684 (2001).
16) J. N. Hancock, T. McKnew, Z. Schlesinger, J. L. Sarrao, and Z. Fisk: Phys. Rev. Lett. **92** (2004) 186405; Phys. Rev. B **73** (2006) 125119.
17) M. Matsunami, H. Okamura, T. Nanba, T. Suemitsu, T. Yoshino, T. Takabatake, Y. Isikawa, and H. Harima: J. Phys. Soc. Jpn. **71** Suppl.(2002) 291.
18) M. Matsunami, H. Okamura, T. Nanba, H. Sugawara and H. Sato: J. Phys. Soc. Jpn. **72** (2003) 2722.
19) M. Matsunami, H. Okamura, T. Nanba, H. Sugawara, H. Sato: J. Magn. Magn. Mater. **272-276** (2004) e41.
20) H. Okamura, T. Michizawa, T. Nanba and T. Ebihara: cond-mat/0609157 (2006).
21) H. Okamura, T. Michizawa, T. Nanba and T. Ebihara: J. Phys. Soc. Jpn. **73** (2004) 2045.
22) N. Tsujii, K. Yoshimura and K. Kosuge: J. Phys.: Condens. Matter **15** (2003) 1993.
23) S. J. Lee, S. Y. Hong, I. R. Fisher, P. C. Canfield, B. N. Harmon, and D. W. Lynch: Phys. Rev. B **61** (2000) 10076.
24) T. Ebihara, S. Uji, C. Terakura, T. Terashima, E. Yamamoto, Y. Haga, Y. Inada and Y. Ōnuki: Physica B **281 & 282** (2000) 754.
25) E. D. Bauer, C. H. Booth, J. M. Lawrence, M. F. Hundley, J. L. Sarrao, J. D. Thompson, P. S. Riseborough and T. Ebihara: Phys. Rev. B **69**, 125102 (2004).
26) C. S. Jee, B. Andraka, J. S. Kim and G. R. Stewart: Phys. Rev. B **43** (1991) 2656.
27) S. L. Bud'ko, Z. Islam, T. A. Wiener, I. R. Fisher, A. H. Lacerda and P. C. Canfield: J. Magn. Magn. Mater. **205** (1999) 53.
28) L. Havela, M. Divic, V. Sechovsky, A. V. Andreev, F. Honda, G. Oomi, Y. Meresse and S. Heathman: J. Alloys and Compounds **322** (2001) 7.
29) A. L. Cornelius, J. M. Lawrence, J. L. Sarrao, Z. Fisk, M. F. Hundley, G. H. Kwei, J. D. Thompson, C. H. Booth and F. Bridges: Phys. Rev. B **56** (1997) 7993.
30) Both $LuInCu_4$ and $YInCu_4$ are semimetals, so they do not serve as reference to $YbInCu_4$. γ_0=8.7 mJ/K^{2}mol is assumed after J. M. Lawrence, P. S. Riseborough, C. H. Booth, J. L. Sarrao, J. D. Thompson and R. Osborn: Phys. Rev. B **63** (2001) 054427.
31) O. Trovarelli, C. Geibel, S. Mederle, C. Langhammer, F. M. Grosche, P. Gegenwart, M. Lang, G. Sparn and F. Steglich: Phys. Rev. Lett. **85** (2000) 626. This work reports a large C_e/T of 1500 mJ/K^{2}mol below 5 K due to NFL formation. We have estimated a Kondo contribution of 100-140 mJ/K^{2}mol by extrapolating the nearly constant C_e/T above 10 K down to T=0.
32) H. S. Jeevan, private communication.
33) I. Umehara, Y. Kurosawa, N. Nagai, M. Kikuchi, K. Satoh and Y. Ōnuki: J. Phys. Soc. Jpn. **59** (1990) 2848.

34) G. A. Costa, F. Canepa and G. L. Olcese: Solic State Commun. **40** (1981) 169.
35) M. J. Besnus, J. P. Kappler and A. Meyer: J. Phys. F; Met. Phys. **13** (1983) 597.
36) γ_0 of YPd$_3$ is used here, C. L. Seaman and M. B. Maple, Physica B **199-200** (1994) 396. LaPd$_3$ has anomalously small γ_0 of 0.28 mJ/K^{2}mol,[35] and does not serve as reference to CePd$_3$. This is supported by the large difference of the lattice constant between CePd$_3$ and LaPd$_3$ (Δa=0.11 Å) compared with that between CePd$_3$ and YPd$_3$ (Δa=0.05 Å).
37) S. Nishigori, H. Goshima, T. Suzuki, T. Fujita, G. Nakamoto, H. Tanaka, T. Takabatake and H. Fujii: J. Phys. Soc. Jpn. **65** (1996) 2614.
38) S. Takayanagi, S. Araki, R. Settai, Y. Ōnuki and N. Mori: J. Phys. Soc. Jpn. **70** (2001) 753.
39) N. Takeda and M. Ishikawa, J. Phys. Soc. Jpn. **69** (2000) 868. This work reports a large C_e/T of 190-380 mJ/mol^{2}K below 2 K due to NFL formation. We have estimated a Kondo contribution of 50−85 mJ/mol^{2}K by extrapolating the C/T vs T^2 plot above 4 K down to 0 K.
40) E. D. Bauer, A. Slebarski, E. J. Freeman, C. Sirvent and M. B. Maple: J. Phys. Condens. Matter **13** (2001) 4495.
41) T. Namiki, Y. Aoki, H. Sugawara and H. Sato: Acta, Physica Polonica B **34** (2003) 1161.
42) F. Marabelli and P. Wachter: Phys. Rev. B **42** (1990) 3307, and references therein.
43) T. Fujita, K. Satoh, Y. Ōnuki and T. Komatsubara: J. Magn. Magn. Mater. **47 & 48** (1985) 66.
44) T. Ebihara, unpublished.
45) N. Tsujii, in preparation.
46) B. Bucher, Z. Schlesinger, D. Mandrus, Z. Fisk, J. Sarrao, J. F. DiTusa, C. Oglesby, G. Aeppli and E. Bucher: Phys. Rev. B **53** (1996) R2948.
47) S. Kimura, J. Sichelschmidt, J. Fersti, C. Krellner, C. Geibel and F. Steglich: J. Magn. Magn. Mater. **272-276** (2004) 36; Phys. Rev. B **74** (2006) 132408.
48) J. Sichelschmidt, V. Voevodin, H. J. Im, S. Kimura, H. Rosner, A. Leithe-Jasper, W. Schnelle, U. Burkhardt, J. A. Mydosh, Yu. Grin and F. Steglich: Phys. Rev. Lett. **96** (2006) 037406.
49) E. J. Singley, D. N. Basov, E. D. Bauer and M. B. Maple: Phys. Rev. B **65** (2002) 161101.
50) M. S. Kim, Y. Echizen, K. Umeo, S. Kobayashi, M. Sera, P. S. Salamakha, O. L. Sologub, T. Takabatake, X. Chen, T. Tayama, T. Sakakibara, M. H. Jung and M. B. Maple: Phys. Rev. B **68** (2003) 054416.
51) J. S. Kim, J. Alwood, G. R. Stewart, J. L. Sarrao and J. D. Thompson: Phys. Rev. B **64** (2001) 134524.
52) H. Kontani and K. Yamada: J. Phys. Soc. Jpn. **66** (1997) 2232.
53) T. Saso and T. Harima: J. Phys. Soc. Jpn. **72** (2003) 1131.
54) G. Czycholl and H. J. Leder , Z. Phys. B Condens. Matter **44** (1981) 59. When a k-independent $\tilde{V}$ is assumed, as in many PAM-based theories on HF compounds, only the c component of the total dos can contribute to $\sigma(\omega)$.